

Mesoscopic bound on anisotropy in itinerant ferromagnets

Piet W. Brouwer and Denis A. Gorokhov

Laboratory of Atomic and Solid State Physics, Cornell University, Ithaca, New York 14853-2501

(Dated: February 2, 2008)

We calculate the anisotropy energy of a single-domain ferromagnetic particle in which the only source of anisotropy is the presence of non-magnetic impurities. We find that such anisotropy takes the form of combined easy-axis and easy-plane anisotropies, with random orientations of the axes. Typically the anisotropy energy is of order $N^{1/2}\hbar/\tau_{\text{so}}$, where N is the number of electrons in the ferromagnetic particle and τ_{so} is the spin-orbit time.

PACS numbers: 75.75.+a, 73.22.-f, 75.30.Gw

Not all magnetization directions are equal for a single-domain ferromagnet. Through magnetic dipole interactions and spin-orbit coupling, the shape of a ferromagnetic particle and the underlying crystal lattice lead to preferred directions for the magnetization [1]. In the absence of these anisotropy sources, how isotropic can a ferromagnetic particle be? We'll answer this question for an itinerant ferromagnet with non-magnetic impurities.

For shape or magnetocrystalline anisotropy the energy gain for a magnetization pointing along a certain 'easy axis' or inside an 'easy plane' is proportional to the number of electrons N contributing to the magnetic moment. Clearly, for the question asked here, there is no such bulk effect. However, for small itinerant ferromagnets, non-magnetic disorder or irregularities in the boundary of the particle break the rotation symmetry on the microscopic scale, thus creating a 'random' anisotropy in the orbital part of electron wavefunctions. This orbital anisotropy affects the magnetization through spin-orbit coupling. The resulting 'mesoscopic' anisotropy does not scale proportional to N , but it is a fundamental lower bound on the anisotropy energy of a ferromagnetic particle. It can be an important contribution in ferromagnetic nanoparticles or in disordered ferromagnetic alloys.

Recently Guéron *et al.* [2] and Deshmukh *et al.* [3] studied the excitation spectra of ferromagnetic particles in the nm size range. The excitation spectrum provides an indirect method to measure the magnetic anisotropy energy [4, 5, 6, 7]. Although shape dominates the magnetic anisotropy in these nanoparticles, the experiments revealed a significant mesoscopic contribution to the anisotropy [2, 3]. Mesoscopic contributions to the magnetic anisotropy energy have also been considered theoretically by Cehovin *et al.* [8] and by Usaj and Baranger [9]. Motivated by the experiments of Refs. 2, 3, these authors studied how the addition of a single electron changes the magnetic anisotropy energy in a ferromagnetic particle with a systematic source of uniaxial anisotropy. The question we ask here is different: it is about the mesoscopic lower limit of the magnetic anisotropy when the magnetic anisotropy energy is dominated by mesoscopic effects. This may be appropriate for the smallest ferromagnetic nanoparticles with low mag-

netocrystalline or shape anisotropy.

We consider an ensemble of ferromagnetic particles, with equal shape, size and concentration of non-magnetic impurities, but with a different configuration of impurities for each particle. All particles in the ensemble are roughly spherical and have no notable magnetocrystalline anisotropy. For such an ensemble, the average free energy F does not depend on the direction of the magnetization $\mathbf{m}$. Hence, the magnitude of the 'mesoscopic' anisotropy must be characterized through its sample-to-sample fluctuations, which can be inferred from the correlation function

$$C(\theta) = \langle F(\mathbf{m}_1)F(\mathbf{m}_2) \rangle \quad (1)$$

where θ is the angle between the magnetization directions $\mathbf{m}_1$ and $\mathbf{m}_2$.

In principle, the ferromagnetic exchange field must be calculated self consistently and at a fixed number of electrons, taking into account the disorder. We simplify the calculation by fixing the exchange field a priori (parallel to $\mathbf{m}$), and by performing the average at a fixed chemical potential μ , rather than a fixed number of particles. The latter simplification does not significantly affect the fluctuations of the free energy [10, 11, 12]. The system under consideration is then described by the single-electron Hamiltonian

$$\mathcal{H} = \mathcal{H}_0 + \mathcal{V}, \quad \mathcal{H}_0 = \frac{p^2}{2m} - E_Z \mathbf{m} \cdot \boldsymbol{\sigma} - \mu, \quad (2)$$

where $E_Z = \mu_B B_{\text{ex}}$ is the Zeeman energy corresponding the exchange field B_{ex} , $\boldsymbol{\sigma}$ is the vector of Pauli matrices, and $\mathcal{V}$ describes the effect of potential scattering and spin-orbit scattering. In a ferromagnet, E_Z is comparable in magnitude to the chemical potential μ .

The free energy F is written as a contribution F_0 in the absence of the potential $\mathcal{V}$, which is isotropic, and a shift ΔF . The shift ΔF is calculated as

$$\begin{aligned} \Delta F = & T \sum_{\mathbf{k}, n} \text{tr} G_0(\omega_n, \mathbf{k}) \mathcal{V}_{\mathbf{k}, \mathbf{k}} + \frac{1}{2} T \sum_{\mathbf{k}_1, \mathbf{k}_2, n} \text{tr} G_0(\omega_n, \mathbf{k}_1) \\ & \times \mathcal{V}_{\mathbf{k}_1, \mathbf{k}_2} G_0(\omega_n, \mathbf{k}_2) \mathcal{V}_{\mathbf{k}_2, \mathbf{k}_1} + \dots, \end{aligned} \quad (3)$$

where $\omega_n = \pi T(2n+1)$, n integer, is the fermionic Matsubara frequency, $G_0(\omega_n, \mathbf{k})$ is 2×2 matrix Green func-

tion corresponding to $\mathcal{H}_0$, and “tr” indicates a trace over the spin degrees of freedom.

The Fourier transform $V_{\mathbf{k}_1, \mathbf{k}_2}$ of the potential $\mathcal{V}$ is

$$\mathcal{V}_{\mathbf{k}_1, \mathbf{k}_2} = v_{\mathbf{k}_2 - \mathbf{k}_1} - i v_{\mathbf{k}_2 - \mathbf{k}_1}^{\text{so}} \boldsymbol{\sigma} \cdot (\mathbf{k}_2 \times \mathbf{k}_1), \quad (4)$$

where v and v^{so} are the impurity potential and the spin-orbit potential, respectively. For the calculation of the correlator $C(\theta)$ we need to perform the ensemble average over the disorder potentials v and v^{so} . We take these to be Gaussian random variables, as is appropriate for a small concentration of impurities,

$$\langle v_{\mathbf{q}} v_{\mathbf{q}'} \rangle = \frac{w_{\mathbf{q}}}{V} \delta_{\mathbf{q}, -\mathbf{q}'}, \quad \langle v_{\mathbf{q}}^{\text{so}} v_{\mathbf{q}'}^{\text{so}} \rangle = \frac{w_{\mathbf{q}}^{\text{so}}}{V} \delta_{\mathbf{q}, -\mathbf{q}'}. \quad (5)$$

The disorder strengths $w_{\mathbf{q}}$ and $w_{\mathbf{q}}^{\text{so}}$ are related to the golden-rule scattering times τ and τ_{so} for elastic scattering and spin-orbit scattering, respectively. We assume that disorder is weak and that scattering processes are predominantly spin-conserving, *i.e.*, $\mu, E_Z \gg \hbar/\tau \gg \hbar/\tau_{\text{so}}$. No assumption is made on the relative magnitude of the spin-orbit scattering rate $\hbar/\tau_{\text{so}}$ and the mean spacing δ between energy levels. For ease of presentation and for technical simplicity, the calculations below are for the case of a ‘half metal’, $E_Z \gg \mu$, for which all electrons in the conduction band have the same spin direction. For the correlation function of the disorder potential we take the simple form

$$w_{\mathbf{q}} = w\theta(2k_F - q), \quad w_{\mathbf{q}}^{\text{so}} = w^{\text{so}}\theta(2k_F - q), \quad (6)$$

where k_F is the Fermi wavevector of the half metal and $\theta(x) = 1$ if $x > 0$ and 0 otherwise. In this simple model, the spin-orbit time for electrons at the Fermi level is given by $\tau_{\text{so}} = 9\pi\hbar^3/2w^{\text{so}}k_F^5m$, where $\hbar k_F$ is the Fermi momentum. Although there will be quantitative differences, our order-of-magnitude estimates continue to hold for a true itinerant ferromagnet in which both minority and majority electrons are present and if the disorder correlator differs from the simple model (6).

Upon performing the disorder average for the correlator (1), one finds that the leading contribution is from a series of ring diagrams, as shown in Fig. 1. Since there is no spin-orbit coupling for forward scattering, the first order ring diagram does not contribute to the mesoscopic anisotropy, whereas the higher order diagrams do.

The second order contribution C_2 is identical to what one would find in standard second order perturbation theory in $\mathcal{V}$, except for the replacement of G_0 by the impurity averaged Green function. This replacement gives rise to a smearing of momenta by an amount of order of the inverse mean free path $1/l$, which is irrelevant for the final result. Hence, we find

$$C_2(\theta) = \sum_{\mathbf{q} \neq 0} \frac{(w_{\mathbf{q}}^{\text{so}})^2}{V^2} \sum_{\mathbf{k}_1 < k_F} \frac{((\mathbf{q} \times \mathbf{k}_1) \cdot \mathbf{m}_1)^2}{\varepsilon_{\mathbf{k}_1} - \varepsilon_{\mathbf{k}_1 + \mathbf{q}}} \times \sum_{\mathbf{k}_2 < k_F} \frac{((\mathbf{q} \times \mathbf{k}_2) \cdot \mathbf{m}_2)^2}{\varepsilon_{\mathbf{k}_2} - \varepsilon_{\mathbf{k}_2 + \mathbf{q}}}, \quad (7)$$

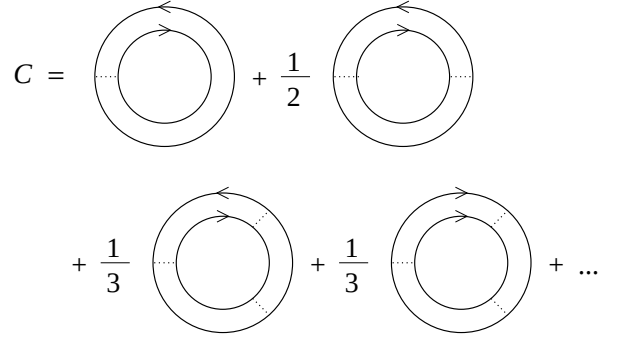


FIG. 1: Diagrammatic representation of $C(\theta)$. The dotted lines represent the impurity average. The solid lines are impurity averaged single-electron Green functions.

plus terms that do not depend on θ . The summations over $\mathbf{q}$, $\mathbf{k}_1$, and $\mathbf{k}_2$ can be done analytically, with the result (again omitting terms that do not depend on θ)

$$C_2(\theta) = -Nc \left(\frac{\hbar \sin \theta}{2\pi\tau_{\text{so}}} \right)^2, \quad (8)$$

where $c = 3(5005 + 24\pi^2)/25025 \approx 0.63$ is a numerical constant and N is the number of electrons contributing to the magnetic moment. Below we show that the contribution to $C(\theta)$ of the higher order diagrams is parametrically smaller than the second-order contribution $C_2(\theta)$. Hence, Eq. (8) contains the dominant contribution to the correlation function $C(\theta)$. Higher order contributions are important only for the dependence of $C(\theta)$ on an applied magnetic field or temperature [13]. However, such dependencies are weak and will not be considered here.

It is important to note that the entire Fermi sea contributes to the magnetic anisotropy fluctuations. This is similar to, *e.g.*, (unscreened) spontaneous dipole moment of a metal grain [13], but different from most other mesoscopic fluctuation effects, such as persistent currents and conductance fluctuations [14], which are determined by the properties of electronic states around the Fermi level only. As a consequence, $C(\theta)$ is not universal; it depends on the details of the impurity potential or on the electronic structure of the ferromagnetic particle. Indeed, in the general case of a ferromagnet with both majority and minority electrons, or for a more general disorder correlator than the simple model (6), the value of the numerical constant c will be different, although the order of magnitude of $C(\theta)$ and the angular dependence will be those of Eq. (8) above.

We now show that the contribution from the higher order diagrams to the correlator $C(\theta)$ is small. Hereto we again consider the case of a half metal, $E_Z \gg \mu$. In order to remove the prefactor $1/n$ from the n th order diagram, $n = 3, 4, \dots$, we calculate $\partial C(\theta)/\partial \theta$ instead of $C(\theta)$. Because $\tau_{\text{so}} \gg \tau$, angular averages for the impurity lines and the single-electron Green functions can be

performed separately for the higher-order diagrams. Neglecting the q -dependence of the disorder correlator in Eq. (5), we then find

$$\frac{\partial C}{\partial \theta} = \frac{\partial C_2}{\partial \theta} + \frac{T}{\pi} \sum_{\mathbf{q}, p > 0} \sum_{\pm} \frac{\partial K_{\pm}(\Omega_p, \mathbf{q}, \theta)}{\partial \theta} \times \frac{\Omega_p K_{\pm}(\Omega_p, \mathbf{q}, \theta)^2}{1 - K_{\pm}(\Omega_p, \mathbf{q}, \theta)}, \quad (9)$$

where $\Omega_p = 2\pi kT_p$ is the bosonic Matsubara frequency and

$$K_{\pm}(\Omega_p, \mathbf{q}, \theta) = \left\langle \frac{\tau_{\text{so}} - \tau(1 \pm \cos \theta)}{\tau_{\text{so}}(1 + \Omega_p \tau - i\hbar \mathbf{q} \cdot \mathbf{k} \tau / m)} \right\rangle_{\mathbf{k}}.$$

Here the brackets $\langle \dots \rangle_{\mathbf{k}}$ denote an angular average over the direction of $\mathbf{k}$. For small frequencies Ω_p and wavevectors $\mathbf{q}$ one can approximate K as

$$K_{\pm}(\Omega_p, \mathbf{q}, \theta) = 1 - \Omega_p \tau - q^2 l^2 / 3 - \frac{\tau}{\tau_{\text{so}}} (1 \pm \cos \theta). \quad (10)$$

When either Ω_p or q are large, one can approximate

$$K_{\pm}(\Omega_p, \mathbf{q}, \theta) \approx \frac{\tau_{\text{so}} - \tau(1 \pm \cos \theta)}{\tau_{\text{so}} \max(\Omega_p \tau, 2ql/\pi)}. \quad (11)$$

The summation over p and q in the region in which both $\Omega_p \tau \lesssim 1$ and $ql \lesssim 1$ can be done using the approximation (10) for K . The zero mode ($\mathbf{q} = 0$) gives a weakly singular contribution to $\partial C / \partial \theta$, which is small in comparison to $C_2(\theta)$, whereas the nonzero modes give a non-singular contribution $\sim V\theta / l^3 \tau_{\text{so}}^2$ for small θ . The remaining part of the summation over p and q is done with the help of Eq. (11) and gives a contribution to $\partial C / \partial \theta$ that is a factor $\sim 1/k_F l \ll 1$ smaller than C_2 .

The above calculation fixes the magnitude of the mesoscopic anisotropy, but it does not fix the form of the anisotropy. In fact, both easy plane and easy axis anisotropies with a random orientation of the plane or the axis give the same angular dependence $C(\theta) \propto \sin^2 \theta$ found from second order perturbation theory. The full angular dependence of $F(\mathbf{m})$ compatible with $C(\theta) \propto \sin^2 \theta$ is one described by an anisotropy tensor H ,

$$F(\mathbf{m}) = \sum_{\alpha, \beta=1}^3 m_{\alpha} H_{\alpha\beta} m_{\beta}. \quad (12)$$

Our previous calculation of the free energy correlator has shown that anisotropy is dominated by second order perturbation theory. Using second order perturbation theory to calculate the full tensor H for a half metal, we find

$$H_{\alpha\beta} = \sum_{\mathbf{q} \neq 0} \sum_{\mathbf{k} < k_F} \frac{|v_{\mathbf{q}}^{\text{so}}|^2}{\varepsilon_{\mathbf{k}} - \varepsilon_{\mathbf{k}+\mathbf{q}}} (\mathbf{k} \times \mathbf{q})_{\alpha} (\mathbf{k} \times \mathbf{q})_{\beta}. \quad (13)$$

A similar but slightly more complicated expression holds for the general case.

From a statistical point of view, the matrix structure of H is the same as that of a matrix $H_{\alpha\beta} = \sum_j u_{j\alpha} u_{j\beta}$, where the $\mathbf{u}_j$ are statistically independent vectors. The elements of such a matrix have Gaussian distributions, the variances of the diagonal elements being twice as large as the variance σ^2 of the off-diagonal elements. Comparing the correlator $C(\theta) = -2\sigma^2 \sin^2 \theta$ one obtains from a Gaussian distribution of H with the microscopic calculation performed above, one finds $\sigma^2 \sim N\hbar^2 / \tau_{\text{so}}^2$.

Changing to principal axes, H can be brought to diagonal form. Denoting the eigenvalues of H by $h_1 < h_2 < h_3$, with corresponding eigenvectors $\mathbf{v}_1$, $\mathbf{v}_2$, and $\mathbf{v}_3$, one can rewrite Eq. (12) as

$$F(\mathbf{m}) = -h_a(\mathbf{m} \cdot \mathbf{v}_1)^2 + h_p(\mathbf{m} \cdot \mathbf{v}_3)^2 + \text{const}, \quad (14)$$

where $h_a = h_2 - h_1$ and $h_p = h_3 - h_2$ are anisotropy energies for easy axis and easy plane anisotropy, respectively. The eigenvalues and eigenvectors of a real symmetric matrix with random Gaussian elements have a distribution that is well known from random matrix theory [15]: The orientation of the eigenvectors $\mathbf{v}_1$, $\mathbf{v}_2$, and $\mathbf{v}_3$ is fully random, whereas the distribution of the three eigenvalues $h_1 < h_2 < h_3$ is

$$P(h_1, h_2, h_3) \propto \prod_{i < j} (h_j - h_i) \prod_i e^{-h_i^2 / 4\sigma^2}. \quad (15)$$

This implies that the distribution of h_a and h_p is

$$P(h_a, h_p) = \frac{8h_a h_p (h_a + h_p) \sqrt{6\pi}}{\sigma^5} e^{-(h_a^2 + h_a h_p + h_p^2) / 6\sigma^2}. \quad (16)$$

In particular, Eq. (16) predicts that the ratio $r = h_a / h_p$ of easy plane to easy axis anisotropies has the distribution

$$P(r) = \frac{27r(1+r)}{8(r^2 + r + 1)^{5/2}}. \quad (17)$$

This result is universal and does not depend on the details of the impurity potential or the electronic structure that affect the magnitude of the mesoscopic anisotropy.

It is instructive to compare the magnitude and the angular dependence of the mesoscopic anisotropy to that of magnetocrystalline anisotropy. For magnetocrystalline anisotropy, the symmetry of the lattice often implies a more complicated angular dependence than that of Eq. (14) [1]. The magnitude of the magnetocrystalline anisotropy scales $\propto \hbar N / \tau_{\text{so}}$, but the numerical prefactor may be small for polycrystalline samples, disordered ferromagnetic alloys, or ferromagnets with a close-to-parabolic dispersion relation. A crude comparison of magnetocrystalline and mesoscopic anisotropy for transition metal magnetic nanoparticles can be made using the following estimates: τ_{so} can be taken comparable to that in Cu [16], $\tau_{\text{so}} \sim 10^{-12}$ s, whereas the magnetocrystalline anisotropy energy is 0.04 meV/atom for Co and

significantly smaller for Fe and Ni [7]. With these estimates, the mesoscopic contribution to the anisotropy energy should become dominant for Co nanoparticles with $\lesssim 10^2$ atoms. For Fe and Ni mesoscopic anisotropy fluctuations start dominating already at larger particle sizes.

Sofar we have dealt with the anisotropy energy $F(\mathbf{m})$ at a fixed number of electrons. This energy determines the size of the energy barrier for magnetization reversal and the low-energy particle-hole and magnetic excitations. An important question for the experiments of Refs. 2, 3 is how much the anisotropy constants h_a and h_p change upon addition of a single electron to the ferromagnetic particle. A theoretical estimate of δh_a and δh_p was given in Refs. [8, 9]. Both theories assumed that there was a systematic source of uniaxial anisotropy, which is appropriate for the non-spherical nanoparticles used in the experiment; Addition of an electron caused a random change $\delta h_a \sim \hbar/\tau_{so} \sim h_a/N$ [9]. Here we briefly address the same question for a ferromagnetic nanoparticle with ‘mesoscopic’ anisotropy only. As we’ll show below, both δh_a and δh_p remain of order $\hbar/\tau_{so}$ [17]. However, since the ‘mesoscopic’ anisotropy is weaker, the relative magnitude of the changes δh_a and δh_p is larger: $\delta h \sim \hbar/N^{1/2}$.

The change of anisotropy energy upon addition of a single electron in an energy level ε follows from the dependence of ε on the magnetization direction $\mathbf{m}$ [8, 9]. The $\mathbf{m}$ -dependence of a single level ε is well described by random matrix theory. For a half metal, there are no spin-flip processes, and one finds that ε is an eigenvalue of the $M \times M$ hermitian matrix

$$\mathcal{H}(\mathbf{m}) = \mathcal{S} + i\sqrt{\frac{\pi\hbar}{4M\tau_{so}\delta}} \sum_{\alpha=1}^3 \mathcal{A}_\alpha m_\alpha, \quad (18)$$

Here δ is the mean level spacing, $\mathcal{S}$ is a real symmetric matrix, and the $\mathcal{A}_\alpha$ are real antisymmetric matrices, $\alpha = 1, 2, 3$. The elements of all matrices are chosen as random Gaussian variables, with the same variance for the off-diagonal elements. Diagonal elements of $\mathcal{S}$ have a double variance. The matrix size M has to be taken to infinity.

In order to find how the addition of a single electron changes the anisotropy energy $F(\mathbf{m})$ for $\mathbf{m}$ close to the direction $\mathbf{m}_0$ at which $F(\mathbf{m})$ is minimal, we expand $\varepsilon(\mathbf{m})$ around $\mathbf{m}_0$. Statistical estimates of the first and second derivatives of ε to $\mathbf{m}$ are relatively straightforward because $H(\mathbf{m}_0)$ and $H(\mathbf{m}) - H(\mathbf{m}_0)$ may be considered statistically independent for small angular deviations. The first and second derivatives of ε to $\mathbf{m}$ are zero on average. The mean square average of the first derivative is $\langle |\partial\varepsilon/\partial\mathbf{m}|^2 \rangle = \hbar\delta/2\pi\tau_{so}$. Typically, the second derivative is of order $\hbar/\tau_{so}$. Using Eq. (14) for $F(\mathbf{m})$, with $h_a, h_p \sim \hbar N^{1/2}/\tau_{so}$, one finds that addition of an electron causes a shift of the preferred magnetization direction $\mathbf{m}_0$ by an angle of order $(\tau_{so}\delta/N\hbar)^{1/2}$. The shifts δh_a and δh_p of the anisotropy constants for easy-axis and easy-plane anisotropy are $\sim \hbar/\tau_{so}$, in agreement with Refs.

8, 9. Note that the expansion of ε around $\mathbf{m}_0$ is valid up to an angle $\theta_{\max} \sim \min[(\tau_{so}\delta/\hbar)^{1/2}, 1]$. Both the angular shift of $\mathbf{m}_0$ and the angular distance of different quantized levels are much smaller than $\theta_{\max}$, so that the expansion used to obtain these estimates is justified.

In conclusion, we have studied magnetic anisotropy in small ferromagnetic particles without shape or magnetocrystalline anisotropy. The presence of non-magnetic impurities and spin-orbit scattering provides a ‘mesoscopic’ lower bound to the particle’s anisotropy energy. This ‘mesoscopic’ magnetic anisotropy is caused by spin-orbit coupling, which connects the orbital anisotropy from non-magnetic impurity scattering to the spin degree of freedom. The strength of the ‘mesoscopic’ anisotropy is of order $N^{1/2}\hbar/\tau_{so}$, where N is the number of electrons contributing to the magnetic moment and τ_{so} is the spin-orbit time, the proportionality constant depending on the details of the electronic dispersion relation and the impurity potential. The angular dependence of the ‘mesoscopic’ anisotropy is a random combination of easy-plane and easy-axis anisotropies.

We would like to thank Kathryn Moler, Dan Ralph, and Bertrand Reulet for discussions. This work was supported by the NSF under grant no. DMR 0334499 and by the Packard Foundation.

-
- [1] J. Kanamori, in *Magnetism*, edited by G. T. Rado and H. Suhl (Academic Press, New York, 1963), vol. 1.
 - [2] S. Guéron, M. M. Deshmukh, E. B. Myers, and D. C. Ralph, Phys. Rev. Lett. **83**, 4148 (1999).
 - [3] M. M. Deshmukh *et al.*, Phys. Rev. Lett. **87**, 226801(R) (2001).
 - [4] C. M. Canali and A. H. MacDonald, Phys. Rev. Lett. **85**, 5623 (2000).
 - [5] S. Kleff, J. von Delft, M. M. Deshmukh, and D. C. Ralph, Phys. Rev. B **64**, 220401(R) (2001).
 - [6] A. Cehovin, C. M. Canali, and A. H. MacDonald, Phys. Rev. B **68**, 014423 (2003).
 - [7] C. M. Canali, A. Cehovin, and A. H. MacDonald, Phys. Rev. Lett. **91**, 046805 (2003).
 - [8] A. Cehovin, C. M. Canali, and A. H. MacDonald, Phys. Rev. B **66**, 094430 (2002).
 - [9] G. Usaj and H. U. Baranger, cond-mat/0407771 (2004).
 - [10] H. Bouchiat and G. Montambaux, J. Phys. (Paris) **50**, 2695 (1989).
 - [11] H.-F. Cheung, E. K. Riedel, and Y. Gefen, Phys. Rev. Lett. **62**, 587 (1989).
 - [12] B. L. Altshuler, Y. Gefen, and Y. Imry, Phys. Rev. Lett. **66**, 88 (1991).
 - [13] R. Berkovits and B. L. Altshuler, Europhys. Lett. **19**, 115 (1992); Phys. Rev. B **46**, 12526 (1994).
 - [14] Y. Imry, *Introduction to mesoscopic physics* (Oxford University Press, 2002).
 - [15] M. L. Mehta, *Random Matrices* (Academic Press, 1991), 2nd ed.
 - [16] L. Piraux *et al.*, J. Magn. Magn. Mater. **156**, 317 (1996).
 - [17] Ref. 9 shows that $\delta h_a \sim h_a/N$ for very weak spin-orbit scattering, $\hbar/\tau_{so} \ll \delta$. The argument given below does not need this assumption.